

SIMPLE CONSTITUTIVE MODELS FOR SOLIDS AND FLUIDS

Manuel Doblaré, Estefanía Peña, and Jose F. Rodríguez

Group of Structural Mechanics and Materials Modelling. Aragón Institute of Engineering Research (I3A). Universidad de Zaragoza, Spain

Keywords: Constitutive laws, solids, fluids, finite deformation, elasticity, hyperelasticity, elastoplasticity, viscoplasticity, viscoelasticity, continuum damage.

Contents

1. Basic Results in Continuum Mechanics
 - 1.1. Kinematics
 - 1.2. Stress Tensors and Balance of Momenta
 - 1.3. Energy Balance Principle and Entropy Inequality
 - 1.4. Fundamental Principles of Constitutive Models
 2. Elastic and Hyperelastic Materials
 - 2.1. Isotropic Hyperelastic Materials
 - 2.2. Constitutive Models for Fiber-Reinforced Hyperelastic Materials
 - 2.3. Examples of Numerical Applications
 3. Elastoplasticity and Viscoplasticity
 - 3.1. Classical Rate-Independent Infinitesimal Strain Plasticity
 - 3.2. Phenomenological Plasticity in Large Deformation Problems
 - 3.3. Viscoplasticity
 4. Viscous fluids And Solids
 - 4.1. Uniaxial Models
 - 4.2. General 3D Viscoelastic Constitutive Models
 - 4.3. Examples of Numerical Application
 5. Continuum Damage Models
 - 5.1. Principles of Continuum Damage Mechanics
 - 5.2. Constitutive Models For Continuum Damage Mechanics of Hyperelastic Materials
 - 5.3. Examples of Numerical Application
- Glossary
Bibliography
Biographical Sketches

Summary

In this chapter we review the fundamentals and the formulation of some simple material constitutive models both for fluids and solids. First, a short review of the main concepts and definitions of Continuum Mechanics is presented, including kinematics and balance principles, in order to make this chapter auto-comprehensive and to fix the terminology and notation. Next, we include the fundamental principles of constitutive models, from a general perspective and without entering in details that have been presented elsewhere in this book, but sufficient to recall the concepts needed in the following sections. Then, we enter in the core of the chapter, discussing the fundamentals of elastic and hyperelastic materials, with especial emphasis in those with fibered microstructure, as well as plastic and viscoplastic solids, viscoelastic liquids and solids and, finally, of

damage-based constitutive models. For a better understanding, in some cases, we have added some illustrating examples and the computational aspects related.

As it is easy to understand, this cannot be a book on rheology, that would need a much longer space, but only an introduction to the main families of constitutive models for engineering materials. In any case, we have tried to be not too restrictive, so fully non-linear kinematics has been assumed in all cases. A much more detailed presentation may be found in the many references included in the chapter.

1. Basic Results in Continuum Mechanics

Below we summarize some basic results of nonlinear continuum mechanics relevant to our subsequent developments. For further details we refer to [11] [31] [32] or [25].

1.1. Kinematics

Let $\mathcal{B} \subset \mathbb{R}^3$ denote the *reference configuration* of a continuum body defined as a set of points located by their respective co-ordinates with respect to a fixed but otherwise arbitrary reference frame $\{\mathbf{X}\}$ at time $t = 0$, and with its particles labeled as $\mathbf{X} \in \mathcal{B}$. For our purposes, it suffices to regard \mathcal{B} as an open bounded set in \mathbb{R}^3 . A *smooth deformation* is a continuously differentiable one to one mapping (as well as its inverse):

$$\chi: \mathcal{B} \rightarrow \mathcal{S} \subset \mathbb{R}^3 \quad (1)$$

which puts into correspondence $\mathcal{B} \subset \mathbb{R}^3$ with some region $\mathcal{S} \subset \mathbb{R}^3$, the *deformed configuration*, in the Euclidean space (see Figure 1). A *motion* is a one-parameter family of deformations, χ_t , parameterized by time, such as, for a fixed time t , (1) represents a deformation mapping between the undeformed and deformed bodies. On the contrary, for a fixed particle \mathbf{X} , (1) gives the trajectory of this particle as a function of time.

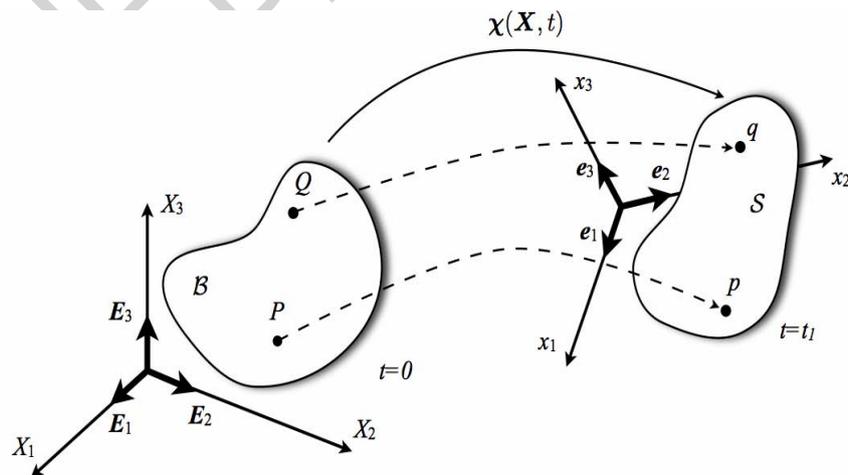


Figure 1. Motion of a deformable body.

In a deformable body, those properties which change along with the deformation of the body might be described either by the evolution of its value along the trajectory of a given material point, *material description* (also known as *Lagrangian description*), or by the change of its value at a fixed location in space occupied by (different for each time instant) particles of the body, *spatial (Eulerian) description*.

The *deformation gradient* is the derivative of the deformation mapping χ . We use the notation (From now on, all the newly defined functions that depend on the motion also depend on time. However, the reference to t will be systematically dropped, except when needed, making such dependence implicit for not complicating the notation.)

$$F(\mathbf{X}) = \nabla_{\mathbf{x}} \chi = \frac{\partial \chi(\mathbf{X})}{\partial \mathbf{X}} = \sum_{i,l=1}^3 F_{il} \mathbf{e}_i \otimes \mathbf{E}_l. \quad (2)$$

The deformation gradient transforms vectors in the reference configuration to vectors in the current configuration, thus describing the change in the relative position of two material particles (or the vector that joins them), and is therefore a two-point tensor,

$$d\mathbf{x} = \mathbf{F}d\mathbf{X}. \quad (3)$$

Similarly, by using the inverse of the deformation gradient, \mathbf{F}^{-1} , material vectors can be written in terms of the corresponding spatial vector as

$$d\mathbf{X} = \mathbf{F}^{-1}d\mathbf{x}. \quad (4)$$

Expressions (3) and (4) are usually referred as *push-forward* and *pull-back* operations of the corresponding vectors, and are expressed, respectively, as $d\mathbf{x} = \chi \circ d\mathbf{X}$, and $d\mathbf{X} = \chi^{-1} \circ d\mathbf{x}$.

By using (3), the infinitesimal volume in the current configuration is given as

$$dv = d\mathbf{x}_1 \cdot (d\mathbf{x}_2 \times d\mathbf{x}_3) = JdV = Jd\mathbf{X}_1 \cdot (d\mathbf{X}_2 \times d\mathbf{X}_3), \quad (5)$$

with $J = \det \mathbf{F}$, the *Jacobian of the deformation*, such that the local condition of impenetrability of matter requires that the local volume ratio

$$J(\mathbf{X}) := \det[\mathbf{F}(\mathbf{X})] > 0. \quad (6)$$

This result allows expressing the conservation of mass as follows

$$dm = \rho dv = \rho JdV = \rho_0 dV \Rightarrow \rho_0(\mathbf{X}) = \rho(\mathbf{X})J(\mathbf{X}). \quad (7)$$

with ρ the current density and ρ_0 the initial density.

Let us consider now an area element in the material configuration, $d\mathbf{S} = dS\mathbf{N}$, and an arbitrary material vector \mathbf{L} not orthogonal to \mathbf{N} . After deformation, these elements become $ds = ds\mathbf{n}$, and $\mathbf{l} = \mathbf{F}\mathbf{L}$. Therefore we can write

$$dv = ds \cdot \mathbf{l} = ds \cdot \mathbf{F}\mathbf{L} = \mathbf{F}^T ds \cdot \mathbf{L}, \quad (8)$$

$$dV = d\mathbf{S} \cdot \mathbf{L}. \quad (9)$$

Using (5) we finally get

$$ds = \mathcal{J}\mathbf{F}^{-T}d\mathbf{S}, \quad (10)$$

known as Nanson's formula.

Let us now consider the change in the inner product of two material vectors $d\mathbf{X}_1$ and $d\mathbf{X}_2$ as they deform through the motion. Using (3), we have

$$d\mathbf{x}_1 \cdot d\mathbf{x}_2 = d\mathbf{X}_1 \cdot \mathbf{F}^T \mathbf{F} \cdot d\mathbf{X}_2 = d\mathbf{X}_1 \cdot \mathbf{C} \cdot d\mathbf{X}_2, \quad (11)$$

where $\mathbf{C} = \mathbf{F}^T \mathbf{F}$ is the *right Cauchy-Green deformation tensor* (Note that \mathbf{C} only operates on material quantities, and is therefore a material tensor.). Similarly, the inner product of two material vectors can be expressed as

$$d\mathbf{X}_1 \cdot d\mathbf{X}_2 = d\mathbf{x}_1 \cdot \mathbf{F}^{-T} \mathbf{F}^{-1} \cdot d\mathbf{x}_2 = d\mathbf{x}_1 \cdot \mathbf{b}^{-1} \cdot d\mathbf{x}_2, \quad (12)$$

where $\mathbf{b} = \mathbf{F}\mathbf{F}^T$ is the *left Cauchy-Green* or *Finger tensor* (In this case, \mathbf{b} only operates on spatial quantities and consequently is a spatial tensor.).

Alternative definitions of strain can be found in terms of the difference in the scalar product of vectors $d\mathbf{X}_1$ and $d\mathbf{X}_2$ in the spatial and material configurations,

$$\frac{1}{2}(d\mathbf{x}_1 \cdot d\mathbf{x}_2 - d\mathbf{X}_1 \cdot d\mathbf{X}_2) = d\mathbf{X}_1 \cdot \mathbf{E} \cdot d\mathbf{X}_2, \quad (13)$$

where,

$$\mathbf{E} = \frac{1}{2}(\mathbf{C} - \mathbf{I}) \quad (14)$$

is the *Lagrange strain* tensor and \mathbf{I} is the second order unit tensor in the initial configuration such as $\mathbf{I}d\mathbf{X} = d\mathbf{X}$. Alternatively, the *Almansi strain* tensor is obtained as

$$\frac{1}{2}(d\mathbf{x}_1 \cdot d\mathbf{x}_2 - d\mathbf{X}_1 \cdot d\mathbf{X}_2) = d\mathbf{x}_1 \cdot \mathbf{e} \cdot d\mathbf{x}_2, \quad (15)$$

with

$$\mathbf{e} = \frac{1}{2}(\mathbf{1} - \mathbf{b}^{-1}). \quad (16)$$

being $\mathbf{1}$ the second order unit tensor in the current configuration.

From (13) and (15) we get

$$d\mathbf{x}_1 \cdot \mathbf{e} d\mathbf{x}_2 = d\mathbf{X}_1 \cdot \mathbf{E} d\mathbf{X}_2, \quad (17)$$

so that the *push-forward* and *pull-back* operations of these strain measures become:

$$\mathbf{e} = \mathbf{F}^{-T} \mathbf{E} \mathbf{F}^{-1} = \chi \circ \mathbf{E}, \quad (18)$$

$$\mathbf{E} = \mathbf{F}^T \mathbf{e} \mathbf{F} = \chi^{-1} \circ \mathbf{e}. \quad (19)$$

When working with incompressible or nearly incompressible materials, it is sometimes useful to consider the multiplicative split of \mathbf{F} into dilatational and distortional (isochoric) parts. This decomposition reads

$$\mathbf{F} = J^{1/3} \bar{\mathbf{F}}. \quad (20)$$

From this, it is now possible to define the isochoric counterparts $\bar{\mathbf{C}}$ and $\bar{\mathbf{b}}$ of the right and left Cauchy-Green deformation tensors (Note that $\det(\bar{\mathbf{F}}) = 1$.)

$$\begin{aligned} \mathbf{C} &= \mathbf{F}^T \mathbf{F} = J^{2/3} \bar{\mathbf{C}}, & \bar{\mathbf{C}} &= \bar{\mathbf{F}}^T \bar{\mathbf{F}}, \\ \mathbf{b} &= \mathbf{F} \mathbf{F}^T = J^{2/3} \bar{\mathbf{b}}, & \bar{\mathbf{b}} &= \bar{\mathbf{F}} \bar{\mathbf{F}}^T. \end{aligned} \quad (21)$$

According to the polar decomposition theorem [31][32], we recall that the deformation gradient at any point $\mathbf{X} \in \mathcal{B}$ can be decomposed as

$$\mathbf{F}(\mathbf{X}) = \mathbf{R}(\mathbf{X}) \mathbf{U}(\mathbf{X}) = \mathbf{V}[\chi(\mathbf{X})] \mathbf{R}(\mathbf{X}), \quad (22)$$

where $\mathbf{R}(\mathbf{X})$ is a proper orthogonal tensor ($\mathbf{R}^T \mathbf{R} = \mathbf{I}$), called the *rotation tensor*, and $\mathbf{U}(\mathbf{X}), \mathbf{V}[\chi(\mathbf{X})]$ are symmetric positive-definite tensors called the *right and left stretch tensors*, respectively, and defined as:

$$\mathbf{C} = \mathbf{U}^T \mathbf{U}, \quad \mathbf{b} = \mathbf{V} \mathbf{V}^T, \quad (23)$$

It is immediate to demonstrate that with the definitions (22)(23), \mathbf{R} is an orthogonal tensor.

$$\mathbf{R}^T \mathbf{R} = \mathbf{U}^{-T} \mathbf{F}^T \mathbf{F} \mathbf{U}^{-1} = \mathbf{U}^{-T} \mathbf{C} \mathbf{U}^{-1} = \mathbf{U}^{-T} (\mathbf{U}^T \mathbf{U}) \mathbf{U}^{-1} = \mathbf{I}, \quad (24)$$

and similarly for the left version of the stretch tensor.

Let now $I_A, (A = 1, 2, 3)$ be the principal invariants of \mathbf{C} (or of \mathbf{b}), defined as

$$\begin{aligned} I_1(\mathbf{C}) &:= \text{tr}[\mathbf{C}] = \mathbf{C} : \mathbf{1}, \\ I_2(\mathbf{C}) &:= \text{tr} \mathbf{C}^{-1} \det \mathbf{C} = \frac{1}{2} (\text{tr}[\mathbf{C}]^2 - \text{tr}[\mathbf{C}^2]), \\ I_3(\mathbf{C}) &:= \det \mathbf{C} = \frac{1}{6} (\text{tr}[\mathbf{C}]^3 - 3 \text{tr}[\mathbf{C}] \text{tr}[\mathbf{C}^2] + 2 \text{tr}[\mathbf{C}^3]). \end{aligned} \quad (25)$$

Since \mathbf{C} is symmetric and positive-definite, by the spectral theorem [31], we can write

$$\mathbf{C} = \sum_{A=1}^3 \lambda_A^2 \mathbf{N}^{(A)} \otimes \mathbf{N}^{(A)}, \quad \|\mathbf{N}^{(A)}\| = 1, \quad (26)$$

where $\lambda_A^2 > 0$ are the eigenvalues of \mathbf{C} , solutions of the characteristic polynomial equation:

$$p(\lambda^2) = \lambda^6 - I_1 \lambda^4 + I_2 \lambda^2 - I_3 = 0, \quad (27)$$

and $\mathbf{N}^{(A)}$ are the associated principal directions fulfilling:

$$\mathbf{C} \mathbf{N}^{(A)} = \lambda_A^2 \mathbf{N}^{(A)}, \quad (A = 1, 2, 3). \quad (28)$$

In (28), $\lambda_A, (A = 1, 2, 3)$, are the *principal stretches* along the *principal directions* $\mathbf{N}^{(A)}$. The push-forward of the principal directions, $\mathbf{N}^{(A)}$, is written as

$$\boldsymbol{\chi} \circ \mathbf{N}^{(A)} = \mathbf{F} \mathbf{N}^{(A)} = \lambda_A \mathbf{n}^{(A)}, \quad \|\mathbf{n}^{(A)}\| = 1. \quad (29)$$

The vectors in the triad $\{\mathbf{n}^{(1)}, \mathbf{n}^{(2)}, \mathbf{n}^{(3)}\}$ are called the *Eulerian principal directions* at $\mathbf{x} = \boldsymbol{\chi}(\mathbf{X}) \in \mathcal{S}$, so that the spectral decomposition of \mathbf{F} takes the form

$$\mathbf{F} = \sum_{A=1}^3 \lambda_A \mathbf{n}^{(A)} \otimes \mathbf{N}^{(A)}. \quad (30)$$

From (23) and (28), the spectral decompositions of the right and left stretch tensors are given by

$$\mathbf{U} = \sum_{A=1}^3 \lambda_A \mathbf{N}^{(A)} \otimes \mathbf{N}^{(A)}, \quad (31)$$

$$\mathbf{V} = \sum_{A=1}^3 \lambda_A \mathbf{n}^{(A)} \otimes \mathbf{n}^{(A)}, \quad (32)$$

respectively, while the spectral decomposition of the rotation tensor takes the form

$$\mathbf{R} = \sum_{A=1}^3 \mathbf{n}^{(A)} \otimes \mathbf{N}^{(A)}. \quad (33)$$

The *material velocity*, denoted by $\mathbf{V}(\mathbf{X}, t)$, is the time derivative of the motion (Do not confuse the material velocity with the left stretch tensor; the context will make clear the particular object considered) :

$$\mathbf{V}(\mathbf{X}, t) = \frac{\partial \chi(\mathbf{X}, t)}{\partial t}. \quad (34)$$

Similarly, the *material acceleration* is defined as the time derivative of the material velocity:

$$\mathbf{A}(\mathbf{X}, t) = \frac{\partial \mathbf{V}(\mathbf{X}, t)}{\partial t} = \frac{\partial^2 \chi(\mathbf{X}, t)}{\partial t^2}. \quad (35)$$

The spatial or Eulerian description can be obtained from the material description by changing the independent variables from material to spatial coordinates of a particle. Accordingly, at any time $t \in [0, T]$, one defines the *spatial velocity* and *acceleration fields*, denoted by $\mathbf{v}(\mathbf{x}, t)$ and $\mathbf{a}(\mathbf{x}, t)$, respectively, by the change of variable formula $\mathbf{x} = \chi(\mathbf{X}, t)$:

$$\mathbf{v}(\chi(\mathbf{X}, t), t) = \mathbf{V}(\mathbf{X}, t), \mathbf{a}(\chi(\mathbf{X}, t), t) = \mathbf{A}(\mathbf{X}, t), \quad (36)$$

or, in compact form,

$$\mathbf{v} = \mathbf{V} \circ \chi^{-1}, \text{ and } \mathbf{a} = \mathbf{A} \circ \chi^{-1}, \quad (37)$$

$$\mathbf{V} = \mathbf{v} \circ \chi \text{ and } \mathbf{A} = \mathbf{a} \circ \chi, \quad (38)$$

where “o” denotes composition (Observe that (38)/(37) are not the push-forward/pull-back operations on the velocity and acceleration, but only the change of variable of those functions associated to the motion)

The material time derivative of a spatial object, such as the spatial velocity, function of the variables $(\mathbf{x}, t) \in \mathcal{S} \subset \mathbb{R}^3 \times [0, T]$, is the time derivative holding the particle (not its

current position) *fixed*. For example, for the spatial velocity, we denote its material time derivative by $\dot{\mathbf{v}}(\mathbf{x}, t)$. Then, by definition,

$$\dot{\mathbf{v}}(\mathbf{x}, t)|_{\mathbf{x}=\chi(\mathbf{X}, t)} := \frac{\partial}{\partial t} \left\{ \mathbf{v}[\chi(\mathbf{X}, t), t] \Big|_{\mathbf{X}=\text{Fixed}} \right\} = \frac{\partial}{\partial t} \mathbf{V}(\mathbf{X}, t) \Big|_{\mathbf{X}=\text{Fixed}} = \mathbf{A}(\mathbf{X}, t). \quad (39)$$

Therefore, by definition of spatial acceleration,

$$\dot{\mathbf{v}}(\mathbf{x}, t) = \mathbf{A}(\mathbf{X}, t) \Big|_{\mathbf{X}=\chi^{-1}(\mathbf{x})} = \mathbf{a}(\mathbf{x}, t), \quad (40)$$

i.e., the material time derivative of the spatial velocity field is the spatial acceleration. In general, if $\boldsymbol{\sigma}(\mathbf{x}, t)$ is a spatial tensor field, by definition, its material time derivative, denoted by $\dot{\boldsymbol{\sigma}}(\mathbf{x}, t)$, is obtained by the formula

$$\dot{\boldsymbol{\sigma}} := \left[\frac{\partial}{\partial t} (\boldsymbol{\sigma} \circ \chi) \right] \circ \chi^{-1} = \frac{\partial \boldsymbol{\sigma}}{\partial t} + \mathbf{v} \cdot \nabla_{\mathbf{x}} \boldsymbol{\sigma} \quad (41)$$

while $\Sigma(\mathbf{X}, t) = \frac{\partial \Sigma}{\partial t}$.

Some additional important material derivatives are the following:

$$\dot{\mathbf{F}} = \frac{\partial \mathbf{F}}{\partial t} = \frac{\partial}{\partial t} [\nabla_{\mathbf{x}} \chi] = \nabla_{\mathbf{x}} \left(\frac{\partial \chi}{\partial t} \right) = \nabla_{\mathbf{x}} \mathbf{V} = \mathbf{L}, \quad (42)$$

where \mathbf{V} is the material velocity field given by (34), and $\nabla_{\mathbf{x}} \mathbf{V}$ is called the *material velocity gradient*. By the chain rule,

$$\nabla_{\mathbf{x}} \mathbf{V} = \nabla_{\mathbf{x}} [\mathbf{v} \circ \chi] = \nabla_{\mathbf{x}} \mathbf{v} \nabla_{\mathbf{x}} \chi = \nabla_{\mathbf{x}} \mathbf{v} \mathbf{F} = \mathbf{I} \mathbf{F}. \quad (43)$$

Combining (42) and (43), we arrive at the following expression for the *spatial velocity gradient* $\mathbf{l} = \nabla_{\mathbf{x}} \mathbf{v}$:

$$\mathbf{l} = \nabla_{\mathbf{x}} \mathbf{v} = \frac{\partial \mathbf{F}}{\partial t} \mathbf{F}^{-1} = \mathbf{L} \mathbf{F}^{-1} = \dot{\mathbf{F}} \mathbf{F}^{-1}. \quad (44)$$

The symmetric part of $\nabla_{\mathbf{x}} \mathbf{v}$, denoted by \mathbf{d} , is called the *spatial rate of deformation tensor*, and its skew-symmetric part is called the *spin* or *vorticity tensor*, denoted by \mathbf{w} . Thus

$$\mathbf{d} = \frac{1}{2} [\nabla_{\mathbf{x}} \mathbf{v} + \nabla_{\mathbf{x}} \mathbf{v}^T] = \frac{1}{2} (\mathbf{l} + \mathbf{l}^T), \quad (45)$$

$$\mathbf{w} = \frac{1}{2} [\nabla_{\mathbf{x}} \mathbf{v} - \nabla_{\mathbf{x}} \mathbf{v}^T] = \frac{1}{2} (\mathbf{l} - \mathbf{l}^T), \quad (46)$$

with

$$\mathbf{l} = \nabla_{\mathbf{x}} \mathbf{v} = \mathbf{d} + \mathbf{w}. \quad (47)$$

The following relationship is also useful:

$$\mathbf{D} = \dot{\mathbf{E}} = \frac{1}{2} \dot{\mathbf{C}} = \frac{1}{2} [\dot{\mathbf{F}}^T \mathbf{F} + \mathbf{F}^T \dot{\mathbf{F}}] = \frac{1}{2} \mathbf{F}^T [(\nabla_{\mathbf{x}} \mathbf{v})^T + \nabla_{\mathbf{x}} \mathbf{v}] \mathbf{F} = \mathbf{F}^T \mathbf{d} \mathbf{F}. \quad (48)$$

Expression (48) justifies the name *material rate of the deformation tensor* given to \mathbf{D} , since $\mathbf{d} = \chi \circ \mathbf{D}$, $\mathbf{D} = \chi^{-1} \circ \mathbf{d}$.

In addition, introducing (18) and (19) into (48) leads to

$$\mathbf{d} = \chi \circ \left(\frac{\partial}{\partial t} (\chi^{-1} \circ \mathbf{e}) \right) = \mathcal{L}_{\chi}[\mathbf{e}]. \quad (49)$$

Hence, the rate of deformation tensor is the push-forward of the time derivative of the pull-back of the Almansi tensor. This operation is known as the *Lie derivative* of a tensor over the mapping χ and it will be used in the following sections, being immediate that \mathbf{d} is the Lie derivative of the Almansi tensor \mathbf{e} .

-
-
-

TO ACCESS ALL THE 98 PAGES OF THIS CHAPTER,
Visit: <http://www.eolss.net/Eolss-sampleAllChapter.aspx>

Bibliography

- [1] Arruda, E.M., and Boyce, M.C. (1993). A Three-Dimensional Constitutive Model for the Large Stretch Behavior of Rubber Elastic Materials. *Journal of the Mechanics and Physics of Solids*, 41(2), 389-412. [This paper gives one of the most widely used constitutive models for rubber materials, also used in soft tissue modeling].
- [2] Baker, M. and Ericksen, J.L., (1954). Inequalities restricting the form of the stress-deformation relations for isotropic elastic solids and Reiner-Rivlin fluids. *Journal of the Washington Academy of Sciences* 44, 33-35. [Important work related to the thermodynamic formulation for elastic solids and Reiner-Rivlin fluids].
- [3] Ball, J.M., (1977). Convexity conditions and existence theorems in nonlinear elasticity. *Archive of Rational Mechanics and Analysis* 63, 337-403. [One of the most significant works related to the existence and unicity of nonlinear elasticity problems].
- [4] Ball, J.M., (1977). Constitutive inequalities and existence theorems in nonlinear elastostatics. In: Knops, R.J. (Ed.), *Nonlinear Analysis and Mechanics: Heriot-Watt Symposium, Vol. I*. Pitman, London,

187-241. [One of the most significant works related to the existence and unicity of nonlinear elasticity problems].

[5] Bertsekas, D.P., (1982). *Constrained Optimization and Lagrange Multiplier Methods*. Academic Press, New York. [This book is an excellent reference in constrained optimization and the Lagrange Multipliers method for optimization].

[6] Boehler, J.P., (1987). *Applications of Tensor Functions in Solid Mechanics*. Springer, Wien. [Reference book for tensor analysis useful in the development of the integral and differential formulation of non-linear continuum mechanics. Invariant formulation of anisotropic solids, representation tensor functions for isotropic and anisotropic solids].

[7] Brewster, D.C., Cronenwett, J.L., Hallett Jr, J.W., Johnston, K.W., Krupski, W.C. and Matsumura, J.S., (2003). Guidelines for the treatment of abdominal aortic aneurysms. *Journal of Vascular Surgery* 37, 1106-1117. [This paper gives the statistics for the mortality caused by the abdominal aortic aneurysms and the morbidity of different treatments of the disease].

[8] Butler, D.L., Guan, Y., Kay, M., Cummings, F. S., and Levy, M., (1992). Location-dependent variations in the material properties of the anterior cruciate ligament. *Journal Biomechanics* 25, 511-518. [This paper investigates the heterogeneity in the mechanical behavior of the anterior cruciate ligament].

[9] Charrier, P., Dacorogna, B., Hanouzet, B. and Laborde, P., (1988). An existence theorem for slightly compressible materials in nonlinear elasticity. *SIAM Journal of Mathematical Analysis* 19, 70-85. [This study shows the validity of Balls results for quasi-incompressible solids when the strain energy function is formulated in terms of the modified invariants].

[10] Christensen, R.M., (1971). *Theory of Viscoelasticity: An Introduction*. Academic Press. New York. [A classical reference book offering a consistent description of the linear theory of the viscoelastic behavior of materials].

[11] Ciarlet, P.G., (1988). *Mathematical elasticity, Vol. I: Three-dimensional elasticity.*, North-Holland, Amsterdam. [Excellent text book with a through description of the mathematical fundamentals of modern non-linear elasticity].

[12] Coleman, B.D. and Noll, W., (1963). The thermodynamics of elastic materials with heat conduction and viscosity. *Archive for rational mechanics and analysis*, 13, 167-178. [A classic work that establishes the fundamental reasoning behind the formulation of constitutive equations in continuum mechanics].

[13] Cordebois, J.P., and Sideroff, F., (1982). Damage induced elastic anisotropy. Mechanical Behaviour of Anisotropic Solids. Proc. EUROMECH Colloque 115, 761-774. [Formulation of the anisotropy induced by damage in initially isotropic elastic solids].

[14] Demiray, H., (1972). A note on the elasticity of soft biological tissues. *Journal of Biomechanical Engineering* 5, 309-311. [This paper proposes a popular isotropic strain energy function used in soft tissue modeling].

[15] Duvaut, G. and Lions, J.L., (1972). *Les Inequations en Mecanique et en Physiques*. Dunod, Paris. [A text book related to the thermodynamic formulation of elastic solids, fluids and electromagnetism].

[16] Dyszlewicz J., (2004). *Micropolar Theory of Elasticity*. Lecture Notes in Applied and Computational Mechanics Vol. 15. Springer Verlag, Heidelberg. [A reference book on the asymmetric theory of elasticity and thermoelasticity].

[17] Elger, D.F., Blackletter, R.S, Budwig, R.S. and Johansen, K.H., (1996). The influence of shape on the stresses in model abdominal aortic aneurysms. *Journal of Biomechanical Engineering* 118, 326-332. [This paper is one of the earliest studies on the influence of shape on the stress distribution in abdominal aortic aneurysms. It proposes a one dimensional model where isotropic behavior is assumed. The conclusions obtained in this work are still used in clinic].

[18] Flory, R.J., (1961). Thermodynamic relations for highly elastic materials. *Transactions of the Faraday Society*, 57, 829-838. [This paper establishes constitutive equations for polymers considering volume and thermal effects under large deformations. Results obtained considering the effect of large strains depart markedly from those obtained from the theory of infinitesimal deformations].

- [19] Fung, Y.C., (1965). *Foundations of Solid Mechanics*. Prentice-Hall International. [An excellent text on solid mechanics, with a major addition to the modern theories of plasticity, and a major revision of the theory of large elastic deformation with finite strains].
- [20] Fung, Y.C., (1993). *Biomechanics: Mechanical Properties of Living Tissue*. Springer Verlag, New York. [A classical reference book internationally accepted as the standard treatment for the study of the mechanics of biological fluids, solids, tissues and organs].
- [21] Gardiner J.C., and Weiss, J.A., (2003). Subject-specific finite element analysis of the human medial collateral ligament during valgus knee loading. *Journal Orthopaedics Research* 21, 1098-1106. [This paper describes a methodology for the stress analysis of patient specific knee ligaments using finite elements and imaging processing techniques].
- [22] Gurtin, M.E., (1981). *An Introduction to Continuum Mechanics*. Academic Press, Orlando. [Reference book in continuum mechanics with reference to the theories of linear elasticity and of ideal, compressible, incompressible, and viscous fluids].
- [23] Hestenes M., (1969). Multiplier and gradient methods. *Journal of optimization theory and applications* 4, 303-320. [This paper establishes the mathematical basis for the optimization algorithm based on the augmented Lagrangian method].
- [24] Hill, R., (1970). Constitutive inequalities for isotropic elastic solids under finite strain. *Proceedings of the Royal Society of London Series A* 314, 457-472. [Analyses the constitutive equations for isotropic solids under finite strain using the notion of conjugate pairs of stress and strain measures].
- [25] Holzapfel, G.A., (2000). *Nonlinear Solid Mechanics. A Continuum Approach for Engineering*. John Wiley & Sons, Chichester. [A reference book in continuum mechanics. The book particularize applications in anisotropic hyperelastic materials, damage and viscoelasticity].
- [26] Hughes, T.J.R., (1984). Numerical Implementation of Constitutive Models: Rate-Independent Deviatoric Plasticity, in *Theoretical Foundations for Large Scale Computations of Nonlinear Material Behavior*, eds S. Nemat-Nasser, R. Asaro, and G. Hegemier. Martinus Nijhoff Publishers, Dordrecht, The Netherlands 29-57. [A reference book with the fundamentals for the numerical implementation of inelastic behavior of solids].
- [27] Humphrey, J.D., (2002). *Cardiovascular Solid Mechanics. Cells, Tissues, and Organs*. Springer-Verlag, New York. [Reference book in soft tissue mechanics. Describes cardiovascular tissue behavior introducing basic analytical, experimental and computational techniques for their study].
- [28] Montagut, E., and Kachanov, M., (1988). On modeling a microcracked zone by weakened elastic-material and on statistical aspects of crack-microcrack interaction. *International Journal of Fracture* 37, R55-R62. [This paper studies the interaction of a crack with a large number of microcracks. The analysis yields analytical expressions for Stress Intensity Factor and the effective elastic moduli].
- [29] Lemaitre, J., and Chaboche, J.L. (1990). *Mechanics of Solid Materials*, Cambridge University Press. [A reference book with a comprehensive description of mechanical and thermal behavior of solids. It describes the theories of elasticity, plasticity, viscoelasticity, viscoplasticity, and fracture].
- [30] Luenberger, D.G., (1984). *Linear and Non linear Programming*. Addison-Wesley Publishing Company, Reading. [Excellent reference book for the study of constrained and unconstrained theory of optimization].
- [31] Malvern, L.E., (2000) *Introduction to the Mechanics of a Continuous Medium*, Prentice Hall International. [Excellent introductory textbook for the theory of continuum mechanics].
- [32] Marsden, J.E. and Hughes, T.J.R., (1994). *Mathematical Foundations of Elasticity*. Dover Publ., New York. [Graduate level book giving different approaches mathematical foundations of three-dimensional elasticity using modern differential geometry and functional analysis].
- [33] Miehe, C. and Keck, J., (2000). Superimposed finite elastic-viscoelastic-plastoelastic stress response with damage in filled rubbery polymers. Experiments, modelling and algorithmic Implementation. *Journal of Mechanics Physics Solids* 48, 323-365. [A phenomenological material model for a superimposed elastic-viscoelastic-plastoelastic stress response with damage at large strains is presented, and considers details of its numerical implementation].

- [34] Mooney, M., (1940). A theory of large elastic deformation. *Journal of Applied Mechanics* 11, 582-592. [The paper introduces the well known strain energy function for rubbers].
- [35] Morrey Jr, C.B., (1952). Quasi-convexity and the lower semicontinuity of multiple integrals. *Pacific Journal of Mathematics* 2, 25-53. [The paper discusses necessary and sufficient conditions on a given function of vector functions in order for its integral on a close domain to be lower semicontinuous].
- [36] Mullins, L., (1947). Effect of Stretching on the Properties of Rubber. *Journal of Rubber Research* 16, 275-289. [This classic experimental work on the study of the effect of cyclic loading on rubbers. This is the paper that first describes the work softening on rubbers subjected to cyclic loading].
- [37] Noll, W., (1958). A mathematical theory of the mechanical of continuous media. *Archives Rational Mechanics Analysis* 2, 199-226. [The paper gives the basis for the constitutive theory for continuum materials (solid and fluids). It introduces a direct notation for developing the concepts in an elegant and concise way. This work represents the basis for the Non-Linear Field Theories of Mechanics paper written by Truesdell and Noll]
- [38] Ogden, R.W., (1972). Large deformation isotropic elasticity I: On the correlation of theory and experiment for incompressible rubberlike solids. *Proceedings Royal Society of London A* 326, 565-584. [This paper introduces the classical Ogden strain energy function for rubbers (incompressible behavior) expressed as a function of the three principal stretches].
- [39] Ogden, R.W., (1972). Large deformation isotropic elasticity II: On the correlation of theory and experiment for compressible rubberlike solid. *Proceedings Royal Society of London A* 328, 567-583. [A strain energy function for compressible solids in terms of principal stretches is introduced in this work. The paper departs from the results obtained by the author for incompressible materials by augmenting the strain energy function with a term function of the density ratio].
- [40] Ogden, R.W., (1996). *Non-linear Elastic Deformations*. Dover Publ., New York. [A classic text book with a meticulous treatment of the theory of finite elasticity. It covers the application of the theory to the solution of boundary-value problems, as well as the analysis of the mechanical properties of solid materials capable of large elastic deformations.]
- [41] Peña, E., Calvo, B., Martínez, M. A. and Doblare, M., (2006). A three-dimensional finite element analysis of the combined behavior of ligaments and menisci in the healthy human knee joint. *Journal of Biomechanics* 39, 1686-1701. [Study the stress distribution in the menisci and ligaments of a healthy human knee. Ligaments are model as quasi-incompressible anisotropic hyperelastic materials, where as menisci are treated as incompressible isotropic].
- [42] Peña, E., Calvo, B., Martínez, M. A. and Doblare, M., (2006). An anisotropic visco-hyperelastic model for ligaments at finite strains: Formulation and computational aspects. *International Journal of Solids and Structures* 44, 760-778. [Thermodynamical formulation and implementation of anisotropic visco-hyperelastic materials. The results are applied to the knee ligament].
- [43] Peña, E., Martínez, M. A., Calvo, B. and Doblare, M., (2006). On the numerical treatment of initial strains in biological soft tissues. *International Journal for Numerical Methods in Engineering* 68(8), 836-860. [Initial stretching in soft tissue is incorporated in the numerical model of the ligament in a healthy knee. Stress field obtained without considering initial stress are compared].
- [44] Perzyna, P., (1966). Fundamental problems in viscoplasticity. *Advances in Applied Mechanics* 9, 243-377. [Comprehensive treatment of the viscoelastic and viscoplastic behavior of solids. Establishes governing and constitutive equations, applying the results to the solution of the dynamic and quasi-static problem of elastic and viscoelastic solids].
- [45] Pioletti, D.P., Rakotomanana, L.R. and Leyvraz, P.F., (1999). Strain rate effect on the mechanical behavior of the anterior cruciate ligament-bone complex. *Medical Engineering and Physics* 25, 95-100. [This paper comprises an experimental study of the mechanical properties of ligament tissue subjected to different strain rates]
- [46] Powell, M.J.D., (1969). A method of nonlinear constraints and minimization problems, in *Optimization*, ed. R. Fletcher. Academic Press, London. [Classic work on constrained optimization regarding the formalism of the augmented Lagrange method for constrained optimization originally introduced by Hestenes].

[47] Rodríguez, J.F., Ruiz, C., Doblaré, M. and Holzapfel, G.A., (2008). Mechanical stresses in abdominal aneurysms: influence of diameter, asymmetry and material anisotropy. *ASME Journal of Biomechanical Engineering* 130, 021-023. [This paper study the effect of shape and material behavior on the stress distribution of idealized abdominal aortic aneurysm. It also introduces a novel anisotropic strain energy function for aneurysmal tissue].

[48] Simo, J. C., (1987). On a Fully Three-Dimensional Finite-Strain Viscoelastic Damage Model: Formulation and Computational Aspects. *Computer Methods in Applied Mechanics and Engineering* 60., 153-173. [This paper describes the thermodynamical formulation, based on internal variables, and numerical implementation for finite-strain viscoelastic solids. Consistent linearization of the problem is fully described].

[49] Simo, J.C., Hughes, T.J.R., (1998). *Computational Inelasticity*. Springer Verlag, New York. [A graduate level text book, well written and easy to follow. The book describes the theoretical foundations of inelasticity, its numerical formulation and implementation. It constitutes a sample of state-of-the-art methodology currently used in inelastic calculations].

[50] Simo, J.C., (1988). A framework for finite strain elastoplasticity based on maximum plastic dissipation and the multiplicative decomposition: Part I. Continuum formulation. *Computer Methods in Applied Mechanics and Engineering* 66, 199-219. [Paper with the thermodynamic formulation of elastoplastic finite strain problems. The work make use of the multiplicative decomposition of the deformation gradient in volumetric and deviatoric components].

[51] Simo, J.C., (1988). A framework for finite strain elastoplasticity based on maximum plastic dissipation and the multiplicative decomposition: Part II. Computational aspects. *Computer Methods in Applied Mechanics and Engineering* 68, 1-31. [This paper discusses the numerical implementation and computational aspects of the finite strain elastoplasticity problem. Consistent linearization of the governing equations is fully discussed].

[52] Simo, J.C., (1992). Algorithms for static and dynamic multiplicative plasticity that preserve the classical return mapping schemes of the infinitesimal theory. *Computer Methods in Applied Mechanics and Engineering* 99, 61-112.

[53] Spencer, A.J.M., (1980). *Continuum Mechanics*. Longman Scientific & Technical, Essex. [Undergraduate book, gives a concise view of continuum mechanics with analysis of deformation and stress; conservation laws as well as the formulation of mechanical constitutive equations]

[54] Taylor, G.I., (1938). Analysis of plastic strain in a cubic cristal, in *Stephen Timoshenko 60th Anniversary Volume*, Ed. J.M. Lessels, Mcmillan, New York. [This paper studies the roll of dislocation motion on the plastic strain of crystalline materials].

[55] Temam, R., (1985). *Mathematical Problems in Plasticity*, Gauthier-Villars, Paris. [This book study, from a mathematical standpoint, the problem of the equilibrium of a perfectly plastic body under certain conditions. The book describes the solution of the two problems in the calculus of variations: the strain problem and the stress problem].

[56] Truesdell, C. and Noll, W., (1965). The Non-Linear Field Theories of Mechanics. *Encyclopedia of Physics*, Ed. S. Flgge, Vol III/3. Springer-Verlag, New York. [A master piece in continuum mechanics. It renders continuums mechanics as beautiful, simple and easy. The book used direct notation and abstract linear algebra to render the exposition clear and simpler and more geometrically and physically illuminating.]

[57] Truesdell, C. and Toupin, R.A., (1960). The Classical Field Theories. *Encyclopedia of Physics*, Ed. S. Flgge, Vol III/1, Springer-Verlag, New York. [A treatise emphasized on the kinematic of deformation. It employs an index notation scheme involving to point tensor field developed by Truesdell. The treatment of constitutive equations is left superficial since it is treated in depth in the NFTM work by Truesdell and Noll]

[58] Valanis, K.C. and Landel, R.F., (1967). The strain-energy function of a hyperelastic material in terms of the extension ratios. *Journal of Applied Physics* 38, 2997-3002. [This paper proposes a strain energy function for rubber based on principal stretch rather than strain invariants. In particular they proposed a separable symmetric strain energy function for incompressible isotropic materials.]

[59] Van de Geest, J.P., Sacks, M.S. and Vorp, D.A., (2006). The effects of aneurysm on the biaxial mechanical behavior of human abdominal aorta. *Journal of Biomechanics* 39, 1324-1334. [Experimental study of the mechanical behavior of aneurysmal and healthy aortic tissue under biaxial loading].

[60] Weiss, J.A, Bradley, N.M. and Govindjee, S., (1996). Finite element implementation of incompressible, transversely isotropic hyperelasticity. *Computer Methods in Applied Mechanics and Engineering* 135, 107-128. [Thermodynamic formulation and finite element implementation of the finite-strain quasi-incompressible anisotropic hyperelastic problem. The paper introduces a novel anisotropic strain energy function for the ligament].

[61] Yeoh, O.H., (1993). Some Forms of the Strain Energy Function for Rubber. *Rubber Chemistry and Technology* 66., 754-771., [The paper introduces a family of polynomial strain energy functions in terms of the right Cauchy-Green deformation tensor for isotropic hyperelastic solids].

[62] Ziegler, H., (1959). A modification of Prager's hardening rule. *Quarterly of Applied Mathematics*, 17, 55-65. [Basic modification to Prager's hardening rule to account for kinematic hardening]

Biographical Sketches

Manuel Doblaré was born in Cordoba (Spain) in July, 1956. He got the degree of Mechanical and Electrical Engineering at the University of Seville (Spain) in 1978 and PhD degree at the Polytechnic University in Madrid (Spain) in 1981. From 1978 to 1982 he was research assistant, when he got the position of assistant professor of Structural Mechanics at the PUM. In 1984, he was appointed as full professor at the Department of Mechanical Engineering of the University of Zaragoza (Spain) where he still teaches. He has occupied the positions of head of the Dept. of Mechanical Engineering (1985-87), dean of the Faculty of Engineering (1993-96) and Director of the Aragon Institute for Engineering Research (2002-07). Currently, he is head of the research group on Structural Mechanics and Materials Modeling (GEMM), and Scientific Director of the National Networking Center on Bioengineering, Biomaterials and Nanomedicine (CIBER-BBN). Prof. Doblaré has been elected as ordinary member of the Spanish Royal Academy of Engineering, the Royal Academy of Mathematics, Physics, Chemistry and Natural Sciences of Zaragoza and the World Council of Biomechanics, and awarded with several distinctions including the Aragon Prize for excellence in research or the Doctorate "Honoris Causa" at the Technical University of Cluj-Napoca (Romania). He was visiting scholar at the Universities of Southampton (Dept. of Civil Engineering-1981) and New York (Courant Institute of Mathematical Sciences-1983) and visiting professor at Stanford University (Division of Applied Mechanics-1990). He is member of different national and international scientific associations and of the editorial boards of several high impact journals where he has published more than 150 papers. He has given plenary, semiplenary and invited lectures in many international congresses and research fori, being internationally recognized in the field of Biomechanics. Prof. Doblaré's research interests are in computational solid mechanics with applications in structural integrity, biomechanics and mechanobiology, with special emphasis in hard and soft tissues modeling, interface behavior and interaction tissue-biomaterial, mechanobiological processes like bone remodeling, bone and wound healing, bone osteointegration or morphogenesis and, finally, tissue engineering.

Estefanía Peña became Associate Professor of the Department of Mechanical Engineering of the University of Zaragoza (Spain) in 2008. From 2001 to 2004 she was lecturer and from 2004 to 2008 Assistant Professor of Structural Mechanics at the UZ. She got the degree of Mechanical Engineering at the University of Zaragoza (Spain) in 2000. She achieved his Ph.D. in Computational Mechanics at the University of Zaragoza in 2004 and spent a post-doctoral stay at the Universities of Southampton in U.K. in 2004 and Joseph Fourier of Grenoble in France in 2005. She is member of Group of Structural Mechanics and Material Modeling of the I3A (Aragón Institute of Engineering Research). Her current research is related to Biomechanics, mainly in the field of Mechanics of Soft Tissues –as blood vessels, muscle, ligament and tendons– mechanical behaviour of biomaterials and prostheses for clinical applications and experimental methods to characterize biological tissues.

José F Rodríguez received his undergraduate degree in Mechanical Engineering from the Universidad Simón Bolívar in Venezuela and his PhD from the University of Notre Dame in 1999. He worked at the Universidad Simón Bolívar from 1999 to 2003, in 2003 he moved to the Universidad de Zaragoza as a

Ramón y Cajal researcher. He is a an associate researcher since 2008. He has conducted research in developing theoretical and computational models of complex nonlinear materials and systems with applications to living tissues and rubber-like solids. Another are of his research is computer electrophysiology and cell biophysics where he studies the electrical activity of the heart and the electro-mechanical interaction in the heart muscle and cardiac cells.

UNESCO – EOLSS
SAMPLE CHAPTERS